

AD-A045 815

MIAMI UNIV FLA DEPT OF MICROBIOLOGY

F/G 8/1

BIOFOULING AND EFFECTS OF ORGANIC COMPOUNDS AND MICROORGANISMS --ETC(U)

SEP 77 S M GERCHAKOV, B SALLMAN

N00014-76-C-0076

NL

UNCLASSIFIED

| OF |  
ADA045815

SEP 77



END  
DATE  
FILMED  
11-77  
DDC



AD A045815

See 1473

12  
B.S.

Microbiology of Power Plant Thermal Effluents  
University of Iowa, September, 1977  
PREPRINT

BIOFOULING AND EFFECTS OF ORGANIC COMPOUNDS AND MICROORGANISMS  
ON CORROSION PROCESSES

Sol M. Gerchakov and Bennett Sallman

Department of Microbiology  
University of Miami School of Medicine  
P.O. Box 520875, Miami, Florida 33152

AD No. \_\_\_\_\_  
DDC FILE COPY

DISTRIBUTION STATEMENT A  
Approved for public release;  
Distribution Unlimited

DDC  
RECEIVED  
OCT 28 1977  
B

BIOFOULING AND EFFECTS OF ORGANIC COMPOUNDS AND MICROORGANISMS  
ON CORROSION PROCESSES

Sol M. Gerchakov and Bennett Sallman

Department of Microbiology  
University of Miami School of Medicine  
P.O. Box 520875, Miami, Florida 33152

---

ABSTRACT

The corrosion rate of metals in natural waters is a function of their metallurgical characteristics and of environmental factors such as temperature, velocity, and chemical makeup of the waters. It was observed that metal surfaces in natural waters became populated with periphytic bacteria in as little as a four-hour exposure time. Subsequent colonization by a variety of microorganisms produced a complex microfouling layer composed of periphytic microorganisms, their extracellular metabolites and cellular breakdown products, and metal corrosion products. The succession of periphytic microorganisms on solid surfaces submerged in natural seawater will be described, and the implication of this primary film in corrosion processes will be discussed.

ACCESSION for	
NTIS	Write Section <input checked="" type="checkbox"/>
DDC	B. II Section <input type="checkbox"/>
UNCLASSIFIED	<input type="checkbox"/>
BY	
DISTRIBUTION/AVAILABILITY CODES	
Dist.	AVAIL. only for SPECIAL
A	

## INTRODUCTION

Biofouling of surfaces immersed in seawater has long been accepted as a natural phenomenon. The development of a fouling layer on a ship's hull, making it heavier and reducing its speed, has placed a heavy burden on the maritime economy since ancient times. It must be recognized, however, that the appearance of visible organisms such as barnacles, tubeworms, mussels, etc. is a relatively late occurrence in a chemical and biological sequence of events.

Solid substrates in contact with seawater will adsorb organic matter on their surfaces (e.g., Zobell, 1943; Smith, 1961; Chave, 1965; Loeb and Neihof, 1977). Whether the resulting organic film is glycoprotein (Baier, 1973) or "humic" (Loeb and Neihof, 1975) in nature, its presence affects the surface charge (Neihof and Loeb, 1974; Loeb and Neihof, 1977) and surface wettability (Dexter, et al., 1975) of the substrate. These properties no doubt play an important role in the subsequent attachment of bacteria to the "conditioned" surfaces (Marshall, 1973).

Bacteria are the first biofouling organisms to attach to surfaces exposed to seawater (Marshall, et al., 1971; Corpe, 1974). While the primary bacterial film on glass and stainless steel surfaces develops with time into a diverse periphytic community (which includes diatoms, filamentous algae, ciliated protozoa, etc.), bacteria continue to increase in numbers (Gerchakov, et al., 1976). In contrast, the surfaces of copper-based alloys, when exposed under the same conditions (Gerchakov, et al., 1977) develop less diverse periphytic communities, with bacteria being the dominating organisms. The ecology of microbial attachment and growth on solid surfaces is reviewed by Corpe (this volume) and Marshall (1976), and will not be discussed here.



The presence of a primary fouling layer composed of living microorganisms, detrital particles, and organic material may attract cyprids of some common barnacles (Barnes, 1970) as well as larvae of other marine animals (Crisp and Ryland, 1960; Meadow and Williams, 1963).

Fouling is particularly troublesome in the more fertile coastal waters, and although it diminishes with distances from the shoreline, it does not disappear in mid-oceanic regions and in the abyssal depths. The increasing utilization of coastal and estuarine waters for cooling purposes in power plants increases the magnitude of the fouling problems. The presence of a limited number of macrofouling agents such as barnacles, tubeworms, etc. on a ship's hull may be tolerated, but their presence on the inner surfaces of a piping system may impede water flow to an unacceptable degree. The existence of a microfouling layer on a ship's hull is of relatively little concern, while its existence as a 250-micron thick layer may result in a 50% reduction in the heat transfer coefficient of a heat exchanger in an ocean thermal energy conversion (OTEC) power plant (Stupian, 1976). In a recent report, Haderlie (1977) reviewed the subject of microfouling in seawater and its significance for OTEC heat exchange surfaces, calling attention to an additional potential problem associated with microfouling -- microbial corrosion.

In this paper, we will review some of the information available on biological corrosion, and discuss possible mechanisms involved.

### MICROBIOLOGICAL CORROSION

The implication of microorganisms in metal corrosion processes was suggested as early as 1891 when Garrett (1891) postulated that the corrosive action of water on lead could be due to ammonia, nitrites, and nitrates produced by bacterial action. Gaines (1910) concluded that underground corrosion of iron and steel structures was partially due to bacterial activity. In fact, the iron bacterium Gallionella ferruginea was isolated from corrosion products on buried steel conduits, and high concentrations of sulfur and organic matter found in the products indicated the presence of sulfur bacteria. Iron in deaerated water does not corrode appreciably, but the corrosion rate in some anaerobic natural environments is abnormally high. Von Wolzogen Kuhr and van der Wlugt (1934) postulated in their classical paper that certain organisms, primarily those of the bacterial genus Desulfovibrio, depolarize the cathode of the corrosion cell by removing hydrogen that accumulates on the surface of iron, and thus promote corrosion under anaerobic conditions. Thomas (1942) noted the growth and accumulation of bacteria in steel water pipes. He proposed that bacteria might be the reason for the degree of corrosiveness of the water, unexplainable by its mineral composition. Drabell (1944), serving as a consulting engineer for the Iowa Electric Power and Light Company, posed in an article the question, "Do bacteria cause condenser tube corrosion?"

A number of reports have implicated a variety of different environments which apparently support microbial corrosion. For example, Thiobacillus concretivorus was isolated in large numbers from corroded concrete obtained from widely separate localities (Parker, 1945a). However, it was found that in an

atmosphere similar to sewer conditions, rapid corrosion occurred only after the environment became favorable to Th. concretivorus growth and the proliferation of the organisms (Parker, 1945b).

Kalinenko (1959) found bacterial colonies on aluminum, brass and bronze plates immersed in natural seawater, and suggested that the bacterial colonies accelerate the electrochemical processes of metal corrosion. Rozenberg and Ulanovskii (1960) stated that bacteria may enhance corrosion of stainless steel in seawater through decreasing the protective effects of cathode polarization, or bacteria may retard corrosion by sedimentation of  $\text{CaCO}_3$  and  $\text{Mg(OH)}_2$  from seawater on the steel surface.

Wacks, et al. (1964) found Desulfovibrio desulfuricans to be responsible for the corrosiveness occurring in aviation gasoline stored in tanks containing small amounts of water. In fact, gasoline stored on culture media inoculated with this organism became corrosive after one week of incubation. Hendey (1964), investigating Cladosporium resinae as a fuel contaminant in kerosene fuel storage tanks and fuel tanks of aircraft, suggested that fungal metabolites are capable of attacking aluminum.

Comparisons were made in the relative corrosiveness of bacteria and fungi for metals in containers being used in space voyages. Tennyson and Brown (1976) compared Rhizopus sp. and Scopulariopsis sp. with pure strains of unidentified species of bacteria isolated from human sources. Visual inspection was made of Aluminum 1100 specimens which were subjected to cultures of these organisms. Fungi were noted to promote corrosion to a considerably greater extent than did bacteria, when Tang instant breakfast drink was used as a substrate. Brown and Pabst (1976) confirmed this observation in their study which included 25 bacterial

and fungal isolates acting on aluminum 1100, aluminum alloys 6061-T6 and 2014-T6, and stainless steel 321, in the presence of Tang or Armour Starr bouillon.

A variety of additional metal substrates have been studied for biological corrosion. Copper was investigated by Thiam (1968) who demonstrated an increased dissolution of this metal in the presence of Aspergillus sp. utilizing soil extract as a medium. Tawadsi and Kemchadse (1972) reported that chrome-manganese steel corroded more rapidly in a variety of pure cultures of heterotrophic marine bacteria including Bacillus tumescens compared with sterile controls. Smith, et al. (1973), however, failed to see any difference between the corrosion rate of 1016 carbon steel in raw and sterile aerated seawater.

Additional literature reports of the biological corrosion of metals may be found in reviews by Rogers (1948), Costello (1969) and Iverson (1972).

### CORROSION MECHANISM

#### General:

Zajic (1969) briefly described corrosion as follows:

"In its broadest concept, corrosion is an electrochemical reaction. It is caused by any kind of heterogeneity at different points on a metal surface. Once a surface makes contact with an electrolyte, however weak, different heterogeneous points show a variance in potential. They develop an electromotive force (emf) and form small local piles or corrosion cells. The more reactive metal acts as the anode, and its atoms pass into the ionic state; at the same time, hydrogen ions are driven back to the less reactive metal which acts as the cathode. When hydrogen forms at the cathode, the corrosion cell becomes polarized. The surface seeks an equipotential state and, as this state is reached, metallic dissolution on the anode follows and continues until the emf decreases and corrosion



stops. Outside forces, of course, can intervene and it is these intervening forces which sustain or increase corrosion."

This description, although cursory in nature, directs attention to outside factors which contribute to corrosion processes. An in-depth discussion of corrosion and its mechanisms can be found elsewhere (e.g., Fontana and Green, 1967; Uhlig, 1971; Shreir, 1976), and will not be presented here.

#### Biological Involvement.

Although the mechanism of biological corrosion is not clear, and the literature on this subject -- specifically as it concerns the seawater environment -- is scant, it can be related to three different considerations:

- (a) Primary effect of microorganisms through the formation of differential concentration cells on the metal surfaces (for example, a respiring periphytic colony of organisms causing a difference in oxygen concentration between its microenvironment and the surrounding area). This will give rise to potential differences, with subsequent corrosion currents between the bacterial colony sites and the surrounding metal surface.
- (b) Direct removal of corrosion products (e.g., a periphytic community removes the oxidized metal (at anodic sites) or utilizes the formed hydrogen (at cathodic sites) will cause the electrochemical corrosion reactions to be biased towards metal dissolution. These respectively may be considered as anodic or cathodic depolarization which will sustain corrosion currents.



- (c) Changes in the chemical environment at the metal/solution interface due to metabolic activity (e.g., changes in pH, or introduction of metabolites) will affect corrosion processes.

Olsen and Szybalski (1950) suggested that aerobic bacteria, such as Gallionella ferruginea, infecting metal surfaces will form microdifferential aeration cells due to a change in concentration of oxygen in the infected areas. As the bacterial colonies grow they form tubercles which further enhance the potential of the differential aeration cells due to poor mixing of water. In fact, Kutznetsov and Verzhbitskaya (1961) observed tuberculation in which species of Leptothrix, Crenothrix, and Spirophyllum ferrugineum participated. Kalinenko (1959) also observed tubercles of bacterial colonies growing on iron, aluminum, copper and bronze plates in seawater.

Anaerobic bacteria are probably the most studied microorganisms in biological corrosion investigations. The enhancing effect of sulfate reducers of the genus Desulfovibrio on corrosion processes was attributed to their ability to remove hydrogen from cathodic sites of corrosion cells. Iverson (1966) presented direct evidence for this cathodic depolarization. Booth and Tiller (1968) demonstrated that Dv. desulfuricans, which possessed hydrogenase activity, stimulated the cathodic reaction, while Desulfotomaculum orientis (hydrogenase-negative) did not. However, Willingham (1966) found that hydrogenase activity of cell-free extracts did not correlate with its corrosiveness to mild steel in seawater.

Similar observations were made in the case of nitrate-reducing bacteria. Mara and Williams (1971) reported that Escherichia coli (hydrogenase-positive) enhanced the corrosion of mild steel, while the effect of Pseudomonas stutzeri

(hydrogenase-negative) was negligible. Ashton, et al. (1973a) investigating the hydrogenase-positive E. coli did not find any relation between nitrate utilization and corrosion of carbon-steel; they concluded that mechanisms other than cathodic depolarization may be operating.

Nelson (1962) challenged the quantitative importance placed on cathodic depolarization as an accelerating factor in anaerobic microbial corrosion. Tiller and Booth (1968), investigating the effect of sulfate-reducing bacteria on aluminum corrosion, concluded that although hydrogenase activity plays a role in the process, the presence of iron sulfide also accelerates corrosion. King and Miller (1971) suggested that the presence of iron sulfide in sulfate-reducing situations is probably more important quantitatively than hydrogenase activity. King, et al. (1973) stated that acceleration of corrosion of mild steel in the presence of sulfur-reducing bacteria is principally due to the formation of iron sulfide, and that hydrogenase activity plays an insignificant role.

Corrosion products such as  $H_2S$  from Desulfovibrio desulfuricans,  $CH_3COOH$  from Clostridium aceticum, and  $H_2SO_4$  from Thiobacillus thiooxidans metabolism, are obvious contributors to corrosion processes. What may not be so obvious is that metabolic products such as mannitol produced in seawater by the action of bacteria on seaweeds appear to accelerate corrosion of brass (Rogers, 1948), and that high molecular weight biomolecules, such as those isolated from cultures of Pseudomonas aeruginosa (Blanchard and Goucher, 1967), are corrosive substances. Staffeldt and Calderon (1967) found that organic acids of the Krebs cycle promoted the corrosion of copper, while many enzymes were found to be considerably less active. Burns, et al. (1967) reported that solutions of various organic acids (citric, fumaric, ketoglutaric, glutaric, maleic, malic, itaconic,

pyruvic, and succinic acid) formed metallic salts of copper, tin, and zinc in sterile solutions. These investigators found that the presence of oxygen was necessary for the formation of these salts. Thus we may infer that the metals were oxidized electrochemically and that the acids removed the oxide film formed. Ashton, et al. (1973b) found acetic, ketoglutaric, succinic, and lactic acids in an anaerobic culture of E. coli where carbon-steel corrosion was enhanced. They suggested that the acid metabolites were responsible for accelerating the corrosion by dissolution of the iron oxide formed on the metal surface. Webb (1975) demonstrated that amino acids accelerate the corrosion rate of copper. Kramer (1976) confirmed this effect of amino acids and found that dicarboxylic acids also enhanced the corrosion of copper.

It is apparent that, although the precise mechanism of microbiological corrosion is ill-understood, microorganisms and their extracellular metabolites exert a significant influence on the otherwise strict electrochemical process of metal oxidation in the environment.

### DISCUSSION

Microfouling and corrosion processes commence immediately upon exposure of a metallic substrate to a natural aquatic environment. In contrast to what is actually occurring in the environment, these two processes have been traditionally treated separately. Furthermore, in spite of the overwhelming evidence for biological involvement in metal corrosion processes, conventional corrosion studies have been conducted with a chronic absence of biological considerations. This apprehension was expressed by Compton (1970) who pointed

out the naiveté of some scientists who consider seawater a simple solution of sodium chloride contaminated with a few additional salts. He also called attention to the so-called "biological factors" which are so often mentioned with regard to the unique corrosive properties of seawater.

For the sake of discussion we may conveniently classify the elements involved in the microfouling/corrosion process into those which are living and those which are not. The non-living ones can be separated into a solid phase and a liquid phase. These three elements (biota, metal, solution) interact with each other, and the product of the three-way interaction gives rise to the microfouling/corrosion phenomenon.

To illustrate this interaction we will refer to Figure 1, where the three elements, the active zones between any two elements, and the zone of interaction among all three elements, are easily identified.

Consider the biota/solution interaction, and ignore the metal/element for the moment. This interaction is governed by the intrinsic properties of the individual elements and, in turn, may alter their own properties. Now consider the solution interacting with the metal, and ignore the biota element for the moment. This interaction is governed by the prevailing conditions at the solid/liquid interface. These conditions are affected by the nature of the interacting elements, and by the interactive process itself.

Introduction of the biota element into this network of interactions and feedbacks system does not simplify matters but brings us closer to the realization of what is happening in the natural environment. If organisms become periphytic (this will be determined by the nature of the organisms and by the prevailing conditions at the solid/liquid interface), their metabolic activities



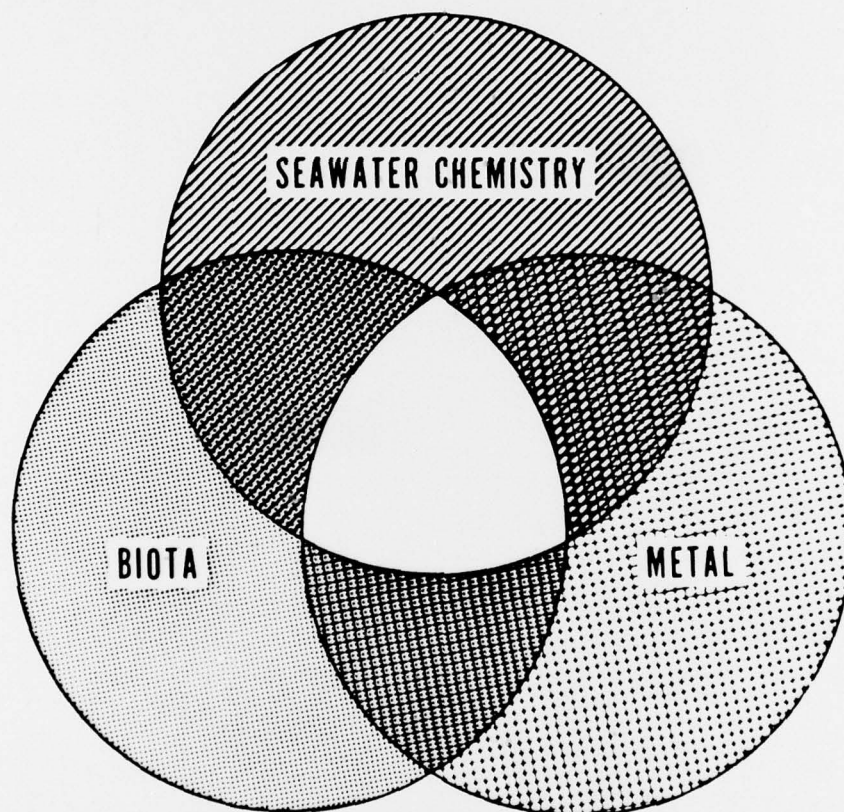


Figure 1: Interaction of the three elements which control the microfouling/corrosion phenomenon in seawater.



may be enhanced (Hendricks, 1974), and they become an additional factor in the system.

From these considerations it is evident that the detailed mechanisms of the fouling/corrosion phenomenon is highly complex and that the much needed understanding of the system will involve the application of a conjoint effort by many branches of science.

#### ACKNOWLEDGEMENTS

We would like to thank many of our colleagues for valuable discussions. Research activities on microfouling/corrosion in our laboratories are supported by the U.S. Office of Naval Research contract N00014-76-C-0076 under project NR 083 300.

## REFERENCES

- Ashton, S.A., R.A. King and J.D.A. Miller. 1973a. Protective film formation on ferrous metals in semicontinuous cultures of nitrate-reducing bacteria. *Br. Corros. J.* 8: 132-136.
- Ashton, S.A., J.D.A. Miller, and R.A. King. 1973b. Corrosion of ferrous metals in batch cultures of nitrate-reducing bacterial. *Br. Corros. J.* 8:185-189.
- Baier, R.E. 1973. Influence of the initial surface condition of materials on bioadhesion. Pages 633-639, in: 3rd Int'l. Congress on Marine Corrosion and Fouling. Northwestern University Press.
- Barnes, H. 1970. A review of some factors affecting settlement and adhesion in the cyprid of some common barnacles. Pages 89-111, in: *Adhesion in Biological Systems*, R.S. Manly (editor). Academic Press.
- Blanchard, G.C. and C.R. Goucher. 1967. Aluminum corrosion processes in microbial cultures. *Electrochem. Technol.* 5: 79-83.
- Booth, G.H. and A.K. Tiller. 1968. Cathodic characteristics of mild steel in suspensions of sulfate-reducing bacteria. *Corr. Sci.* 8: 583-600.
- Brown, L.R. and G.S. Pabst. 1976. Biodeterioration of stainless steel and aluminum alloys. Pages 375-882, in: *Proc. 3rd Int'l. Biodeg. Symp.* J.M. Sharpley and A.M. Kaplan, editors. Applied Science Publishers.
- Burnes, J.M., E.E. Staffeld, and O.H. Calderon. 1967. Corrosion caused by organic acids reacting with three metals, with special emphasis on Krebs cycle acids. *Develop. Ind. Microbiol.* 8: 327-334.
- Chave, K.E. 1965. Carbonate association with organic matter in seawater. *Science* 148: 1723-1724.
- Compton, K.G. 1970. The unique environment of seawater and its effect on corrosion of metals. *Corrosion* 26: 448-449.
- Corpe, W.E. 1974. Periphytic marine bacteria and the formation of microbial films on solid surfaces. Pages 397-417, in: *Effect of the Ocean Environment on Microbial Activities*. R.R. Colwell and R.Y. Morita, editors. University Park Press.
- Costello, A.J. 1969. The corrosion of metals by microorganisms: A literature survey. *Int. Biodegr. Bull.* 5: 118-191.

- Crisp, D.J. and J.S. Ryland. 1960. Influence of filming and of surface texture on the settlement of marine organisms. *Nature* 185: 119.
- Dexter, S.C., J.D. Sullivan, J. Williams, and S.W. Watson. 1975. Influence of substrate wettability on the attachment of marine bacteria to various surfaces. *Appl. Microbiol.* 30: 298-308.
- Drabelle, J.M. 1944. Do bacteria cause condenser tube corrosion? *Power Plant Engr.* 48: 122-124.
- Gaines, R.H. 1910. Bacterial activity as a corrosive influence in the soil. *Ind. Eng. Chem.* 2: 128-130.
- Garrett, J.H. 1891. "The Action of Water on Lead." H.K. Lewis, London.
- Gerchakov, S.M., D.S. Marszalek, F.J. Roth, and L.R. Udey. 1976. Succession of periphytic microorganisms on metal and glass surfaces in natural seawater. Pages 205-211, in: *Proc. 4th Int'l. Congress on Marine Corrosion and Fouling*. Juan-les-Pins, Antibes, France.
- Gerchakov, S.M., D.S. Marszalek, F.J. Roth, B. Sallman, and L.R. Udey. 1977. OTEC Biofouling and Corrosion Symposium (in press).
- Fontana, M.G. and N.D. Greene. 1967. "Corrosion Engineering." McGraw-Hill, N. Y.
- Haderlie, E.C. 1977. The nature of primary organic films in the marine environment and their significance to Ocean Thermal Energy Conversion (OTEC) heat exchange surfaces. Report No. NPS-68Hc 77021. Naval Post Graduate School, Monterey, Ca.
- Hendey, N.I. 1964. Some observations on Cladosporium resinae as a fuel contaminant and its possible role in the corrosion of aluminum alloy fuel tanks. *Trans. Br. Mycol. Soc.* 47: 467-475.
- Hendricks, S. 1974. Sorption of heterotrophic and enteric bacteria to glass surfaces in the continuous culture of river water. *Appl. Microbiol.* 28: 572-578.
- Iverson, W.P. 1966. Direct evidence for the cathodic depolarization theory of bacterial corrosion. *Science* 151: 986-988.
- Iverson, W.P. 1972. Biological corrosion. Pages 1-42, in: *Advances in Corrosion Science*. Vol. 2, M.G. Fontana and R.W. Staehle, editors. Plenum Press.
- Kalinenko, V.O. 1959. Bacterial colonies on metal plates in seawater. *Microbiologiya* 28: 698-702.
- King, R.A. and J.D.A. Miller. 1971. Corrosion by the sulfate reducing bacteria. *Nature* 233: 491-492.

- King, R.A., J.D.A. Miller, and D.S. Wakerley. 1973. Corrosion of mild steel in cultures of sulfate-reducing bacteria. *Br. Corr. J.* 8: 89-93.
- Kramer, D.A. 1976. The corrosion kinetics of copper in aqueous amino acid and carboxylic acid solutions. Ph.D. dissertation. University of Miami.
- Kuhr, von Wolzogen, C.A.H. and van der Vlugt. 1934. Graphitization of cast iron as an electrochemical process in anaerobic soils. *Water (The Hague)* 18: 147-165.
- Kutznetsov, V.V. and L.V. Verzhbitskaya. 1961. On the role of microorganisms in iron corrosion in water. *Microbiologiya* 30: 511-514.
- Loeb, G.I. and R.A. Neihof. 1975. Marine conditioning films. *Adv. Chem. Series* 145: 319-335.
- Loeb, G.I. and R.A. Neihof. 1977. Adsorption of an organic film at the platinum-seawater interface. *J. Mar. Res.* 35: 283-291.
- Mara, D.D. and D.J.A. Williams. 1971. Corrosion of mild steel by nitrate reducing bacteria. *Chem. Ind.* 21: 566-567.
- Marshal, K.C. 1973. Mechanism of adhesion of marine bacteria to surfaces. Pages 625-632, in: *Proc. 3rd Int'l. Congress on Marine Corrosion and Fouling*. Northwestern University Press.
- Marshal, K.C. 1976. *Interfaces in microbial ecology*. Harvard University Press.
- Marshal, K.C., R. Stout, and R. Mitchell. 1971. Selective sorption of bacteria from seawater. *Can. J. Microbiol.* 17: 1413-1416.
- Meadow, R.S. and G.B. Williams. 1963. Settlement of *Spirobis borealis* daudin larvae on surfaces bearing films of microorganisms. *Nature* 198: 610-611.
- Neihof, R.A. and G.I. Loeb. 1974. Dissolved organic matter in seawater and the electric charge of immersed surfaces. *J. Mar. Res.* 32: 5-12.
- Nelson, E.E. 1962. (Discussion of the paper "Microbiological corrosion in waterfloods" by J.M. Sharpley. *Corr.* 17: 386t-390t). *Corrosion* 18: 247t-248t.
- Olsen, E. and W. Szybalski, 1950. Aerobic microbiological corrosion of water pipes. *Corrosion* 6: 405-414.
- Parker, C.D. 1945a. The corrosion of concrete. I. The isolation of a species of bacterium associated with the corrosion of concrete exposed to atmospheres containing hydrogen sulfide. *J. Exp. Biol. Med. Sci.* 23: 81-89.



- Parker, C.D. 1945b. The corrosion of concrete. II. The function of Thiobacillus concretivorus in the corrosion of concrete exposed to atmospheres containing hydrogen sulfide. J. Exp. Biol. Med. Sci. 23: 90-98.
- Rogers, T.H. 1948. The promotion and acceleration of metallic corrosion by microorganisms. J. Inst. Metals 75: 19-38.
- Rozenberg, L.A. and I.B. Ulanovskii. 1960. Growth of bacteria during cathode polarization of steel in seawater. Microbiologiya 29: 521-523.
- Shreir, L.L. 1976. Corrosion. Newness-Butterworths, London.
- Smith, C.A., K.G. Compton and F.H. Coley. 1973. Aerobic marine bacteria and the corrosion of carbon steel in seawater. Corr. Sci. 13: 671-685.
- Smith, J.B. 1961. Preliminary investigation of the association of organic material and carbon dioxide with sedimentary particles. Ph.D. dissertation. Texas A&M University.
- Staffeldt, E.E. and O.H. Calderon. 1967. Possible degradation of metals by microorganisms. Dev. Ind. Microbiol. 8: 321-326.
- Stupian, G.W. 1976. Potential fouling of OTEC heat exchangers by marine organisms. Report No. ATR-77(9401-01)-1. Aerospace Corporation, El Segundo, Ca.
- Tawadsi, F. and S. Remchadse. 1972. The corrosive action of heterotrophic marine bacteria. Pages 114-115, in: Biodeterm. of Materials, Vol. 2. A.H. Walters and E.H. Hueck-Van der Plas, editors. Halsted Press.
- Tennyson, J.M. and L.R. Brown. 1976. The microbial degradation of aluminum 1100. Pages 883-888, in: Proc. 3rd Int'l. Biodegrad. Symp. J.M. Sharpley and A.M. Kaplan, editors. Applied Science Publishers.
- Thiam, M.L. 1968. Dissolution of copper by Aspergillus. Ann. Inst. Pasteur. 114: 468-473.
- Thomas, A.H. 1942. Role of bacteria in corrosion. Water works and Sewage 89: 367-372.
- Tiller, A.K. and G.H. Booth. 1968. Anaerobic corrosion of aluminum by sulfate-reducing bacteria. Corro. Sci. 8: 549-555.
- Uhlig, H.H. 1971. Corrosion and corrosion control. 2nd Edition, John Wiley and Sons, N.Y.
- Wacks, A.M., S. Bentur, Y. Kott, M. Babitz and A.B. Stern. 1964. Aviation gasoline corrosiveness caused by sulfate reducing bacteria. Ind. Engr. Chem. Process. Des. Dev. 3: 65-69.



- Webb, C.A. 1975. A polarization resistance study of copper corrosion kinetics in aqueous chloride and amino acid solutions. Ph.D. dissertation. University of Miami.
- Willingham, C.A. 1966. Studies on the mechanisms of mild steel corrosion in the marine environment with special reference to the sulfate reducing bacteria. Ph.D. dissertation. University of Miami.
- Zajic, J.E. 1969. Microbial Biogeochemistry, page 225. Academic Press, N.Y.
- ZoBell, C.E. 1943. The effect of solid surfaces upon bacterial activity. J. Bacteriology 46: 39-56.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

REPORT DOCUMENTATION PAGE		READ INSTRUCTIONS BEFORE COMPLETING FORM
1. REPORT NUMBER (6)	2. GOVT ACCESSION NO.	3. RECIPIENT'S CATALOG NUMBER (9)
4. TITLE (and Subtitle) Biofouling and Effects of Organic Compounds and Microorganisms on Corrosion Processes		5. TYPE OF REPORT & PERIOD COVERED Scientific Paper, (Preprint)
7. AUTHOR(s) Gerchakov, S.M. and B. Sallman		8. CONTRACT OR GRANT NUMBER(s) (15) N00014-76-C-0076
9. PERFORMING ORGANIZATION NAME AND ADDRESS University of Miami, Department of Microbiology P.O. Box 520875 Miami, Florida 33152		10. PROGRAM ELEMENT, PROJECT, TASK AREA & WORK UNIT NUMBERS NR 083 300
11. CONTROLLING OFFICE NAME AND ADDRESS Office of Naval Research (Code 484) Arlington, Virginia 22217		12. REPORT DATE (11) September 1977
14. MONITORING AGENCY NAME & ADDRESS (if different from Controlling Office) (10) Sol M. / Gerchakov Bennett / Sallman (12) 21p.		13. NUMBER OF PAGES 18
16. DISTRIBUTION STATEMENT (of this Report) Distribution of this document is unlimited.		15. SECURITY CLASS. (of this report) Unclassified
17. DISTRIBUTION STATEMENT (of the abstract entered in Block 20, if different from Report)		15a. DECLASSIFICATION/DOWNGRADING SCHEDULE
18. SUPPLEMENTARY NOTES Presented at the Microbiology of Power Plant Thermal Effluent Symposium, University of Iowa, September 1977.		
19. KEY WORDS (Continue on reverse side if necessary and identify by block number) Biofouling Biological Corrosion		
20. ABSTRACT (Continue on reverse side if necessary and identify by block number) The corrosion rate of metals in natural seawater is a function of their metal- lurgical characteristics and of environmental factors such as temperature, velocity, and chemical makeup of the waters. It was observed that metal surfaces in natural waters became populated with periphytic bacteria in as little as a four-hour exposure time. Subsequent colonization by a variety of microorganisms produced a complex (continued on reverse)		

DD FORM 1 JAN 73 1473

EDITION OF 1 NOV 65 IS OBSOLETE  
S/N 0102-014-6601

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE (When Data Entered)

LB

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)

20. Abstract (continued)

microfouling layer composed of periphytic microorganisms, their extracellular metabolites and cellular breakdown products, and metal corrosion products. This paper reviews some of the information available on biological corrosion, and discusses possible mechanisms involved.

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE(When Data Entered)